



RECIPE

P3296-A Potash Feldspar	34.80
P3346-A Calcium Carbonate	18.30
P3309 China Clay	9.60
P3337-C Quartz	31.90
P3304 Bentonite	5.50

COLOURANTS ETC.

P3410 Red Iron Oxide	7.69
P3402 Cobalt Carbonate	0.55
P3415 Manganese Dioxide	1.10



	Seger.	% Anal.
CoO	0.0175	0.36
MnO	0.0479	0.94
Fe2O3	0.1833	8.13

Al : Si	9.6089
Coef.of Exp.	9.3676
Surf.Tens.	361.268
Clay Body	
Colour	
Glaze Type	
Opacity	
Texture	
Stability	
Fit	

	Seger	% Anal.
KNO	0.2408	6.29%
CaO	0.6909	10.77%
MgO	0.0028	0.03%
BaO		
ZnO		
PbO		
Li2O		
SrO		
Al2O3	0.3892	11.02%
P2O5		
B2O3		
SiO2	3.7400	62.45%
TiO2		
ZrO2		
K2O	0.2391	6.26%
Na2O	0.0017	0.03%

Comment

Date Last Changed

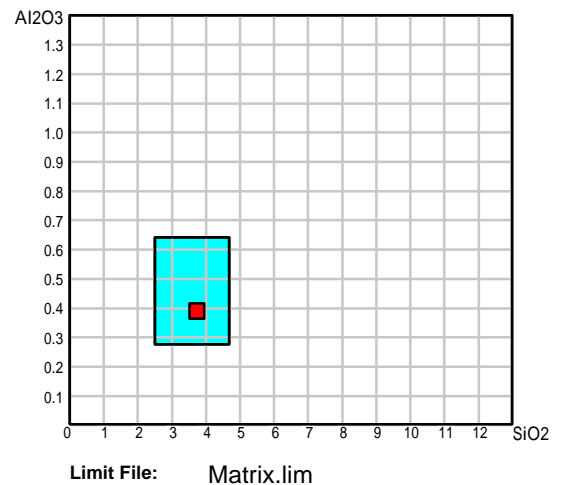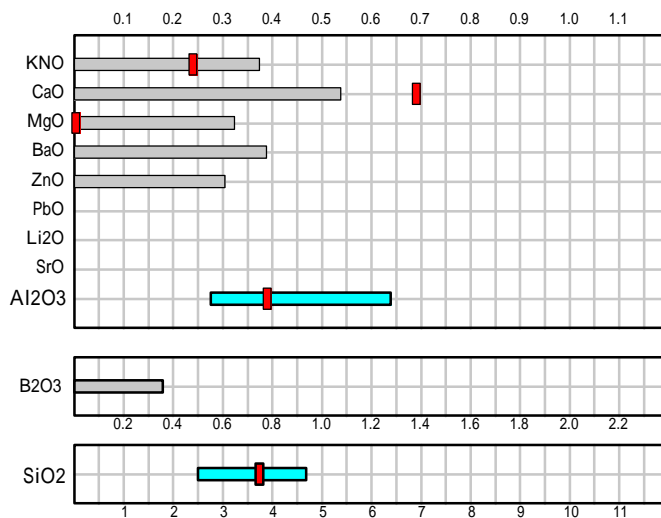

金藝美供

香港 九龍 彌敦道760號 東海大廈526室 電話 : +852 81072038 +852 27892038